



AFRL-RQ-WP-JA-2012-0260

**BULK NANOCOMPOSITE $\text{LaCo}_5/\text{LaCo}_{13}$ MAGNETS
(POSTPRINT)**

Yuhui Shen

University of Dayton Research Institute

Zafer Turgut and Meiqing Huang

UES, Inc.

John Horwath

Electromechanical Branch

Power Division

AUGUST 2012

Approved for public release; distribution unlimited.

See additional restrictions described on inside pages

STINFO COPY

© 2011 American Institute of Physics

**AIR FORCE RESEARCH LABORATORY
AEROSPACE SYSTEMS DIRECTORATE
WRIGHT-PATTERSON AIR FORCE BASE, OH 45433-7542
AIR FORCE MATERIEL COMMAND
UNITED STATES AIR FORCE**

REPORT DOCUMENTATION PAGE				Form Approved OMB No. 0704-0188	
The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.					
1. REPORT DATE (DD-MM-YY) August 2012		2. REPORT TYPE Journal Article Postprint		3. DATES COVERED (From - To) 27 July 2009 – 23 September 2010	
4. TITLE AND SUBTITLE BULK NANOCOMPOSITE LaCo ₅ /LaCo ₁₃ MAGNETS (POSTPRINT)				5a. CONTRACT NUMBER In-house	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER 62203F	
6. AUTHOR(S) Yuhui Shen (University of Dayton Research Institute) Zafer Turgut and Meiqing Huang (UES, Inc.) John Horwath (AFRL/RQPM)				5d. PROJECT NUMBER 3145	
				5e. TASK NUMBER N/A	
				5f. WORK UNIT NUMBER Q0JE	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) <div style="display: flex; justify-content: space-between;"> <div style="width: 30%;"> University of Dayton Research Institute Dayton, OH 45432 ----- UES, Inc. 4401 Dayton-Xenia Road Dayton, OH 45432 </div> <div style="width: 65%;"> Electromechanical Branch (AFRL/RQPM) Power Division Air Force Research Laboratory Aerospace Systems Directorate Wright-Patterson Air Force Base, OH 45433-7542 Air Force Materiel Command, United States Air Force </div> </div>				8. PERFORMING ORGANIZATION REPORT NUMBER AFRL-RQ-WP-JA-2012-0260	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) Air Force Research Laboratory Aerospace Systems Directorate Wright-Patterson Air Force Base, OH 45433-7542 Air Force Materiel Command United States Air Force				10. SPONSORING/MONITORING AGENCY ACRONYM(S) AFRL/RQPM	
				11. SPONSORING/MONITORING AGENCY REPORT NUMBER(S) AFRL-RQ-WP-JA-2012-0260	
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution unlimited.					
13. SUPPLEMENTARY NOTES Journal article published in the <i>Journal of Applied Physics</i> , Vol. 109, 2011. PA Case Number: 88ABW-2010-5855; Clearance Date: 03 Nov 2010. This technical paper contains color. © 2011 American Institute of Physics. The U.S. Government is joint author of the work and has the right to use, modify, reproduce, release, perform, display, or disclose the work.					
14. ABSTRACT The effects of processing parameters and composition on the magnetic properties and microstructure of nanocrystalline La-Co-based hard magnetic materials were investigated. Bulk nanocomposite LaCo ₅ /LaCo ₁₃ magnets were fabricated by mechanical alloying of LaCo ₅ and La ₂ Co ₇ powder mixtures and subsequent hot pressing at 580–810 °C. A high coercive field (H _c) of over 16 kOe with a smooth demagnetization curve was obtained in a composition range of 25–30 wt. % La ₂ Co ₇ when hot-pressed at 660–760 °C. Microstructural investigations indicated that the magnets consist of a primary LaCo ₅ phase with grain sizes of 200–400 nm, coexisting with 20–100 nm grains of LaCo ₁₃ located both at the grain boundaries and within the hard LaCo ₅ grains.					
15. SUBJECT TERMS rare earth magnets, permanent magnets					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT: SAR	18. NUMBER OF PAGES 10	19a. NAME OF RESPONSIBLE PERSON (Monitor) John C. Horwath 19b. TELEPHONE NUMBER (Include Area Code) N/A
a. REPORT Unclassified	b. ABSTRACT Unclassified	c. THIS PAGE Unclassified			

Bulk nanocomposite $\text{LaCo}_5/\text{LaCo}_{13}$ magnets

Y. Shen,¹ Z. Turgut,² J. Horwath,³ and M. Huang^{2,a)}¹Magnetics Laboratory, University of Dayton, Dayton, Ohio 45469, USA²UES Inc, AFRL, 4401 Dayton-xenia RD, Dayton, Ohio 45432, USA³Air Force Research Laboratory, Wright-Patterson AFB, Ohio 45433, USA

(Presented 15 November 2010; received 23 September 2010; accepted 8 December 2010; published online 15 April 2011)

The effects of processing parameters and composition on the magnetic properties and microstructure of nanocrystalline La-Co based hard magnetic materials were investigated. Bulk nanocomposite $\text{LaCo}_5/\text{LaCo}_{13}$ magnets were fabricated by mechanical alloying of LaCo_5 and La_2Co_7 powder mixtures and subsequent hot pressing at 580–810 °C. A high coercive field (H_c) of over 16 kOe with a smooth demagnetization curve was obtained in a composition range of 25–30 wt. % La_2Co_7 when hot-pressed at 660–760 °C. Microstructural investigations indicated that the magnets consist of a primary LaCo_5 phase with grain sizes of 200–400 nm, coexisting with 20–100 nm grains of LaCo_{13} located both at the grain boundaries and within the hard LaCo_5 grains.

© 2011 American Institute of Physics. [doi:10.1063/1.3562446]

I. INTRODUCTION

Among the intermetallic compounds of the La-Co system, the LaCo_5 phase (hexagonal CaCu_5 -type structure) has a strong uniaxial magnetocrystalline anisotropy field (H_A) of 175 kOe and a high Curie temperature (T_c) of 840 K.¹ The value of saturation magnetization, $4\pi M_s$, of 900 G (G) is relatively low.¹ The NaZn_{13} -type LaCo_{13} phase has a higher Co content, resulting in a larger magnetization of 1300 G and a higher T_c of 1297 K.² The cubic structure and relatively low H_A of the LaCo_{13} phase (~ 12 kOe) compared to that of the LaCo_5 phase makes it unsuitable as a permanent magnet.^{3,4} However, composites of LaCo_5 (hard)/ LaCo_{13} (soft), similar to those of the FePt (hard)/ Fe_3Pt (soft) system, could be a promising permanent magnet system for high temperature applications. Previous research showed that sintered microscale LaCo_5 magnets had coercivities, H_c , of 11–12 kOe at room temperature.⁵ Recently, a nanoscale LaCo_5 -based powder with a record high H_c of 17 kOe was produced by mechanical milling and subsequent annealing.⁶

In the present study, bulk nanocomposites of $\text{LaCo}_5/\text{LaCo}_{13}$ were fabricated by mechanical alloying followed by hot pressing. The effects of compositional variations and processing parameters on the magnetic properties and microstructure were investigated.

II. EXPERIMENTAL DETAILS

The LaCo_5 and La_2Co_7 alloys were prepared by arc melting then crushed to a powder with particle sizes less than 250 μm . Powder mixtures with different weight ratios of La_2Co_7 between approximately 0 to 50% (La content of 32 to 36 wt.%), were mechanically milled for 16 hs using a Spex 8000M high energy mill to form amorphous precursors. Samples were then hot pressed (HP) at temperatures between 580–810 °C for 30 s under 25 kpsi load to form fully dense,

crystalline nanocomposite magnets. Magnetic properties at room temperature were measured by a closed-loop hysteresis graph. The crystal structure, phase fractions, and microstructure were characterized by x-ray diffraction (XRD) with Cu radiation, scanning electron microscopy (SEM), and transmission electron microscopy (TEM).

III. RESULTS AND DISCUSSION

The magnetic properties exhibited a strong dependence on hot pressing temperature and composition. Figure 1(a) shows typical demagnetization curves of the bulk La-Co magnets, with the La_2Co_7 ratio ranging from 0 to 50 wt. %. Among the studied compositions, a high H_c of over 15 kOe with a smooth demagnetization curve was obtained for the samples with La_2Co_7 weight fraction of 25–30% (La content of 34–34.5 wt. %) when hot pressed at 760 °C. The ratio of the remanence magnetization (M_r) to the magnetization at 1.5 T, $M_r/M(1.5 \text{ T})$, is roughly 0.9. The ratio H_k/H_c (where H_k is the reversal field when the moment $4\pi M$ drops down to 90% of the remanent $4\pi M_r$) quantifies the squareness of the

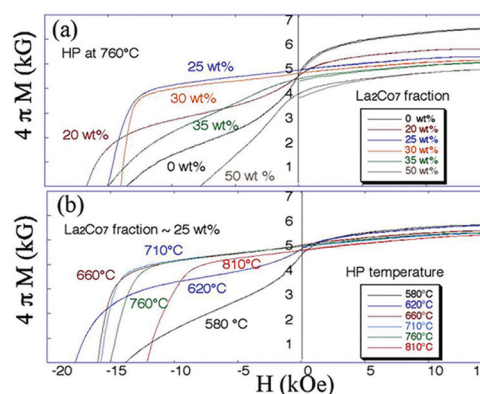


FIG. 1. (Color online) (a) Demagnetization curves of the bulk La-Co magnets as a function of La_2Co_7 weight fraction after hot pressing at 760 °C, and (b) as a function of hot pressing temperature for 25 wt. percent La_2Co_7 .

^{a)}Electronic mail: Meiqing.Huang@wpafb.af.mil.

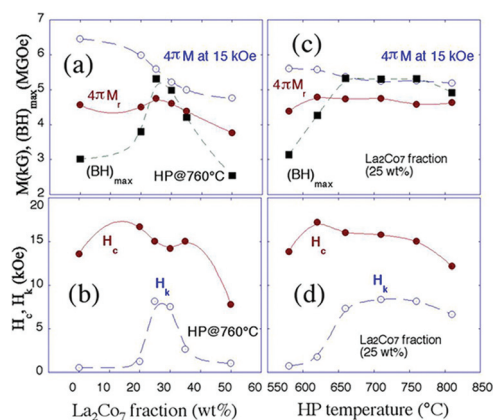


FIG. 2. (Color online) (a), (b) Magnetic properties of the bulk La-Co magnets as a function of La_2Co_7 weight fraction after hot pressing at 760 °C, and (c), (d) as a function of hot pressing temperature for 25 wt. percent La_2Co_7 .

M-H loop. Values of H_k/H_c for these samples are close to 0.54 at room temperature. Magnets that are outside of this composition range exhibited lower H_c values and a shoulder in their demagnetization curves, indicative of a magnetically uncoupled structure. A similar uncoupling behavior is also observed for magnets that were hot pressed below 660 °C [Fig. 1(b)]. An optimum HP temperature window for the magnets with La_2Co_7 weight fraction of 25% is determined to be 660–760 °C. For higher processing temperatures, the coercivity is significantly reduced, while maintaining a single phase behavior. The overall hard magnetic properties with respect to composition and HP temperatures are summarized in Figs. 2(a)–2(d), respectively. In general, magnets that are hot pressed at 660–760 °C and contained 25–30 wt. percent of La_2Co_7 exhibited the highest H_c up to 16.6 kOe, with maximum energy products, $(BH)_{max}$, of approximately 5 MGOe. Outside of these optimal conditions, a shoulder in the demagnetization curve or lower H_c values significantly reduces $(BH)_{max}$.

X-ray diffraction and SEM indicated that the magnets are comprised of a multi-phase structure. The hot pressed samples were ground to a powder for XRD, with the resulting patterns presented in Fig. 3. The patterns indicate the

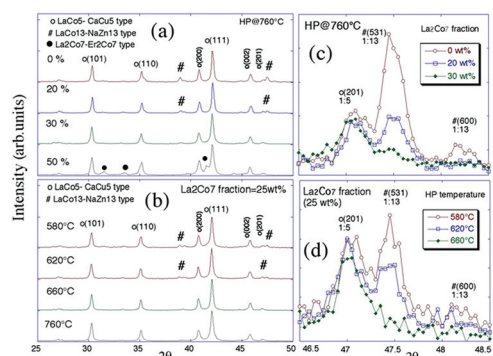


FIG. 3. (Color online) X-ray diffraction patterns of random powders as a function of La_2Co_7 weight percent for samples hot pressed at 760 °C (a), and as a function of hot press temperature for samples containing 25 wt. % La_2Co_7 (b). (c) and (d) show reflections from 1:13 phase (a) and (b), respectively, in detail.

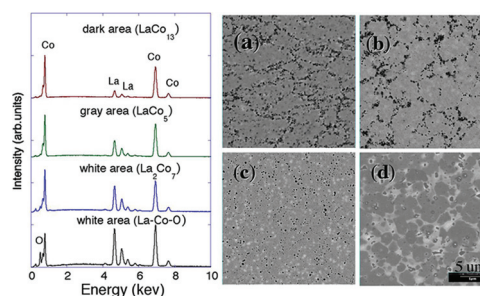


FIG. 4. (Color online) SEM/BSE images and corresponding EDS patterns for the bulk La-Co magnets with La_2Co_7 weight fractions of (a) 0%, (b) 20%, (c) 30%, and (d) 50% after hot pressing at 760 °C. The three composition areas are: (1) dark areas (Co-rich $LaCo_{13}$ phase), (2) gray areas ($LaCo_5$ phase), and (3) lighter areas (La-rich La-Co or La-O phases).

presence of three magnetic phases: (1) the $LaCo_5$ phase that dominates the structure of all magnets, (2) the $LaCo_{13}$ phase, detected as a minor phase in some of the samples, and (3) a La-rich phase in an Er_2Co_7 structure, detected when the La_2Co_7 content increases up to 50 wt %. The La-rich phase has a low $H_A \approx 50$ kOe (see Ref. 7), resulting in a decrease of the coercivity. Figure 3(a) shows the patterns for magnets hot pressed at 760 °C as a function of La_2Co_7 weight percent. The reflections shown in Fig. 3(c) indicate that the 1:13 phase decreases with increasing La_2Co_7 weight fraction, becoming almost undetectable at 30%. Similar behavior is observed as the HP temperature is increased for the magnets with the La_2Co_7 content of 25 wt. % [Figs. 3(b) and 3(d)]. The small amount of the 1:13 phase gradually decreases and almost disappears at temperatures of 660 °C and above. Existence of the magnetically uncoupled behavior in the demagnetization curves of the hot pressed magnets should be related to the presence of this detectable 1:13 phase. Even though it cannot be detected by XRD, magnets with a smooth demagnetization curves also contain a finely distributed small fraction of 1:13 phase evidenced by the SEM and TEM analysis. As it is discussed in detail by Kneller and Hawig,⁸ the phase fraction and distribution of the low anisotropy phase greatly influences the coupling behavior.

Figure 4 depicts the SEM back-scattered electron (SEM/BSE) images and corresponding energy dispersive spectroscopy (EDS) patterns of the bulk La-Co magnets as a function of weight fraction for samples hot pressed at 760 °C. The

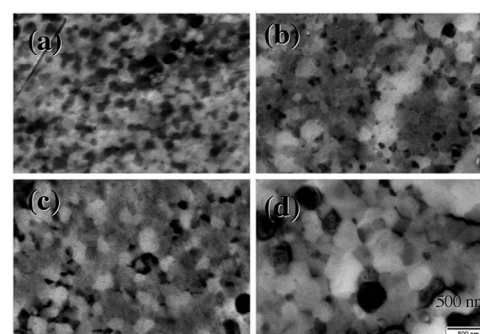


FIG. 5. SEM/BSE images for the bulk La-Co magnets with the La_2Co_7 weight fraction of 25% after hot pressing at (a) 580 °C, (b) 660 °C, (c) 710 °C, and (d) 760 °C.

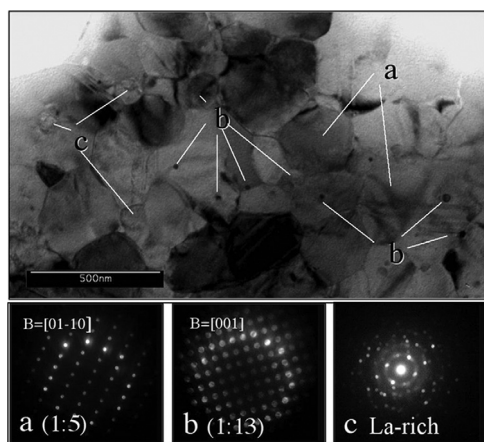


FIG. 6. TEM image and NBE diffraction patterns of bulk La-Co magnet with La_2Co_7 weight fraction of 25% after hot pressing at 660 °C; (a) LaCo_5 - CaCu_5 type; $B=[01-10]$, (b) LaCo_{13} - NaZn_{13} type; $B=[001]$, and (c) La rich phases.

contrast in the images indicates increasing La concentration from dark to light. EDS indicates that the dark areas correspond to the Co-rich LaCo_{13} phase, the gray areas correspond to the LaCo_5 phase, and lighter areas correspond to the La-rich La-Co or La-O phases. The microstructure is highly dependent on weight percent of La_2Co_7 , where Fig. 3(c) shows the best distribution of the dark 1:13 phase in the gray 1:5 phase. This is consistent with the magnetization measurements, which indicated the optimum microstructure for exchange-spring behavior occurs for La_2Co_7 fractions of 25–30wt%. Increasing the La_2Co_7 content [Fig. 3(d)] results in an increase in the amount of the La-rich phase (white areas)

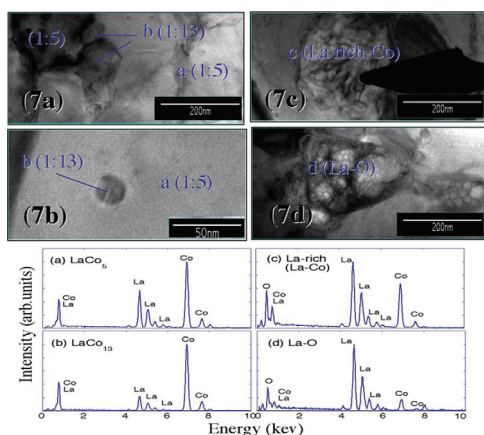


FIG. 7. (Color online) TEM images and corresponding EDS patterns of the phases present in the bulk La-Co magnet with La_2Co_7 weight fraction of 25% after hot pressing at 660 °C. (a) LaCo_5 , (b) LaCo_{13} , (c) La rich La-Co, and (d) La-O.

as well as an increase in the grain size. The magnetization measurements show that this results in a lower H_c and/or a lower H_k . Figure 5 shows the SEM/BSE images of the bulk La-Co magnets with the La_2Co_7 weight fraction of 25% as a function of HP temperature. The amount of Co rich LaCo_{13} phase (dark areas) reduces and their distribution improves as the HP temperatures increases from 580 to 660 °C, resulting in a better coupling behavior. Higher HP temperatures beyond 760 °C cause the grains to grow larger, resulting in a decrease of H_c . The La_2O_3 phase was also detected at higher HP temperatures, causing a reduction in H_c .

Microstructural details of the 660 °C hot pressed magnet, with La_2Co_7 content of 25 wt. %, are presented in Figs. 6 and 7. TEM/EDS and nanobeam-electron (NBE) diffraction results suggest that the magnet exhibits a nanocomposite structure composed of four distinct phases: (a) the 1:5, (b) the 1:13, (c) the La-rich La-Co ($\sim\text{La}_2\text{Co}_7$), and (d) the La-O (near La_2O_3 stoichiometry) phases. These results are consistent with the findings from the XRD and SEM studies. The main LaCo_5 phase (grain sizes of 200–400 nm) coexists with the soft LaCo_{13} phase (20–100 nm), located both at grain boundaries [see Fig. 7(a)], and within the hard 1:5 grains [see Fig. 7(b)]. The observed hard magnetic properties are attributed to the high anisotropy field and uniform grain size of the LaCo_5 phase, as well as its exchange coupling to the LaCo_{13} phase. It is worth noting that the finely distributed La-rich La-Co and the La-O phases (or precipitates) have a subgrain structure [see images in Fig. 7(c) and 7(d)] and they are located among the 1:5 and 1:13 grains. The effects of these La-rich phases are not readily known. However, if they are paramagnetic in nature they are expected to act as pinning sites to impede the domain walls. If they are ferromagnetic, regardless of their anisotropy field, they are small enough to participate in the exchange coupling activity as a third party.

In summary, bulk $\text{LaCo}_5/\text{LaCo}_{13}$ nanocomposite magnets with maximum H_c values of 16 kOe have been successfully synthesized. The microstructure and magnetic properties are sensitive to initial powder weight ratios and hot pressing temperatures. This system shows promise as a permanent magnet system for high temperature applications.

¹W. A. J. J. Velge and K. H. J. Buschow, *J. Appl. Phys.* **39**, 1717 (1968).

²K. H. J. Buschow, *Rep. Prog. Phys.* **40**, 1179 (1977).

³S. A. Nikitin *et al.*, *J. of Alloys and Comp.* **367**, 266 (2004).

⁴M. Q. Huang *et al.*, *J. Appl. Phys.* **83**, 6471 (1998).

⁵J. W. Walkiewicz and M. M. Wong, "Magnetic properties of alloys containing Lanthanum, Cobalt, Copper and Magnesium," Bureau of Mines Report of Investigations (1982).

⁶H. Okumura, F. Zhang, and G. C. Hadjipanayis, *J. Appl. Phys.* **91**, 6146 (2002).

⁷K. H. J. Buschow, *J. the Less-Common Metals*, **33**, 311 (1973).

⁸E. Kneller and R. Hawig, *IEEE Trans. Magn.* **27**, 3588 (1991).